arXiv:1207.2457v1 [cond-mat.supr-con] 10 Jul 2012

Unveiling the vortex-glass phase transition in superconducting Ba(Fe$_{0.9}$Co$_{0.1}$)$_2$As$_2$

G. Prando,[1, *] R. Giraud,[1] M. Abdel-Hafiez,[1] S. Aswartham,[1] A. U. B. Wolter,[1] S. Wurmehl,[1] and B. Büchner[1, 2]

[1]*Leibniz-Institut für Festkörper- und Werkstoffforschung (IFW) Dresden, D-01171 Dresden, Germany*
[2]*Institut für Festkörperphysik, Technische Universität Dresden, D-01062 Dresden, Germany*

(Dated: July 11, 2012)

Measurements of magnetic ac susceptibility were performed on a single crystal of superconducting Ba(Fe$_{0.9}$Co$_{0.1}$)$_2$As$_2$ close to the conditions of optimal doping. The extremely high quality of the investigated sample allows the detection of dynamical-scaling behaviour associated with a glass transition for the flux lines in the limit of weak degree of quenched disorder. The corresponding critical exponent and glass critical temperature are precisely quantified for different values of the polarizing magnetic field up to 9 Tesla. The field-dependence of the critical exponent rules out any dimensionality crossover for the vortex state in the investigated range, suggesting instead a gradual transition among qualitatively different types of glassy phases. In particular, a Bragg-like glass is likely to be gradually disordered towards a more amorphous state with increasing the magnetic field.

PACS numbers: 74.25.Uv, 74.25.Wx, 74.70.Xa

The possibility of exploring the physical properties of the mixed Shubnikov phase in type-II superconductors over a wide range of external thermodynamical parameters has lead to the most important achievements of the research on high-T_c materials [1, 2]. The physics of vortices (or fluxoids, each one bringing a quantized unit $\Phi_0 = hc/2e$ of magnetic field flux) is indeed of great interest on the level of fundamental research, where the system is typically modeled as a statistical ensemble of filaments interacting both among themselves and with the defects of the crystalline environment [1, 2]. In this respect, a strongly debated topic concerns the actual occurrence of a real phase transition between different regions in the magnetic field – temperature ($H - T$) phase diagram of the superconducting state where dissipation processes occur or not [3]. An impressive amount of experimental data, especially from transport measurements of current-voltage ($I-V$) characteristics, have been interpreted in terms of scaling arguments strongly suggesting that the scenario of critical processes is holding (for an early review about scaling in high-T_c cuprate superconductors see Ref. 4).

The discovery of high-T_c type-II superconductivity in Fe-based pnictides [5, 6] has recently renewed the interest for the investigation of the vortex state. These materials are known to possibly bridge the gap between high-T_c cuprates and low-T_c alloys. Besides T_c values intermediate with respect to what is typically reported for the aforementioned two classes of materials, in fact, pnictides join both high upper critical magnetic fields H_{c2} and almost isotropic superconducting properties quantified by low values for the anisotropy parameter γ. Emblematic compounds in this respect are those belonging to the so-called 122 family, displaying $\mu_0 H_{c2}$ as high as 50 Teslas while γ as low as 2 [6]. Several experimental results have been reported in the literature about the detailed features of vortex pinning in connection with the flux motion, the positioning of the irreversibility line on the $H - T$ phase diagram and the estimates of critical currents (see, for instance, Refs. 7–13). Nevertheless, to the best of our knowledge, the data have been rarely examined in terms of the critical behaviour associated with a phase transition to a glassy-like state for the vortices, but rather in terms of thermally activated processes in the strong-disorder limit. Criticality is in fact expected to be hidden by high degrees of quenched disorder in the system, including the extrinsic effects of boundaries between different grains in powder samples. In this Letter, we report on ac susceptibility measurements performed on an extremely high-quality single crystal of Ba(Fe$_{0.9}$Co$_{0.1}$)$_2$As$_2$. Results are qualitatively and quantitatively different from what has been observed from similar measurements performed on other pnictide superconductors and strongly hint that the scenario of a vortex-glass phase transition is at work. The extremely low degree of quenched disorder in the investigated sample, moreover, allows to infer interesting insights into the detailed evolution of the glassy-phase towards more amorphous configurations upon increasing the static magnetic field.

The investigated single crystal is of rectangular shape with dimensions $2a = 1.7 \pm 0.025$ mm, $2b = 3.0 \pm 0.025$ mm and $2c = 0.05 \pm 0.025$ mm (where the height $2c$ is parallel to the c crystallographic axis), following the notation reported in Ref. 14. Details about the crystal-growth procedure and preliminar characterization can be found in Ref. 15. According to our resistivity data, the sample is in conditions of almost-optimal doping with a value for the critical temperature in zero magnetic field estimated as $T_c(0) \simeq 23.5$ K. Measurements of magnetic ac susceptibility χ_{ac} as a function of T were performed by means of a Physical Properties Measurement System (PPMS, Quantum Design) allowing to apply polarizing static magnetic fields $\mu_0 H_{dc}$ as high as 9 T. Measurements were always performed by slowly warming the sample after a field-cooled (FC) procedure across T_c. The

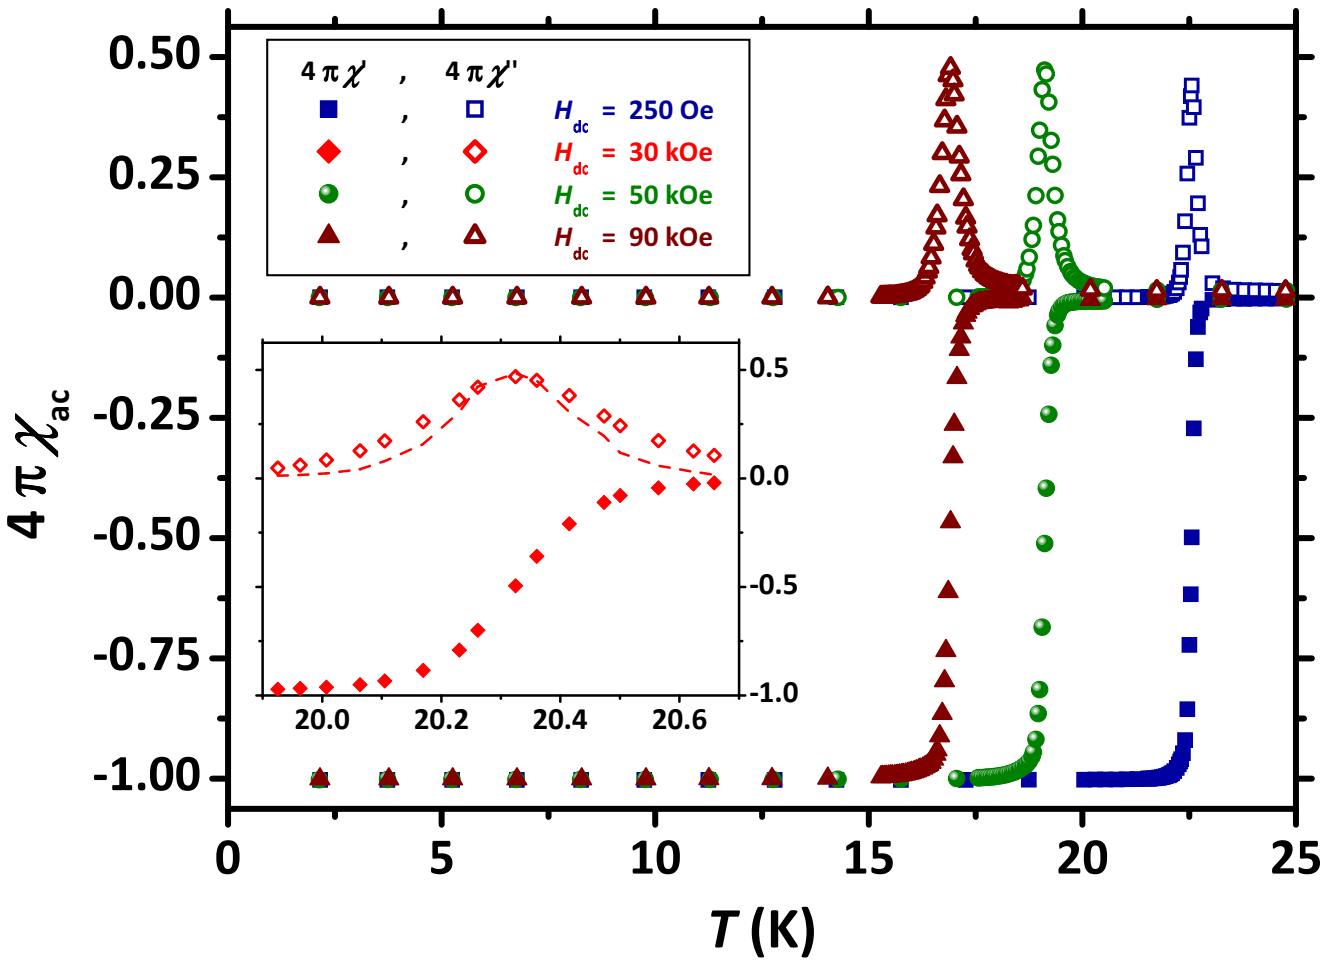

FIG. 1: (Color online) Main panel: $\chi_{\rm ac}$ vs. T data for both real and imaginary components at $\nu_{\rm m} = 9685$ Hz and at different $H_{\rm dc}$ (after correction for the demagnetization factor). Inset: zoom of data for $H_{\rm dc} = 30$ kOe around the step-like drop of the real component. The dashed line represents the derivative of $\chi'_{\rm ac}$ with respect to T (arb. units).

amplitude of the alternating magnetic field $H_{\rm ac}$ was kept fixed to 1 Oe during all the measurements while the working frequency $\nu_{\rm m}$ was swept between 10 and 10^4 Hz. Both $H_{\rm dc}$ and $H_{\rm ac}$ were applied parallel to the crystallographic c-axis (within an accuracy of ± 1°). For this geometry, the demagnetization factor is estimated as $D_{\rm m} \simeq 0.95$ (see Ref. 14). The intrinsic susceptibility $\chi_{\rm i}$ is then obtained from the measured one $\chi_{\rm m}$ following the relation $1/\chi_{\rm i} = 1/\chi_{\rm m} - 4\pi D_{\rm m}$ (where volume units have been assumed for both $\chi_{\rm i}$ and $\chi_{\rm m}$). From now on, only the demagnetization-corrected $\chi_{\rm i}$ data will be considered and the subscript i will be dropped for the sake of clarity.

Fig. 1 shows a step-like diamagnetic response of the real part of the magnetic ac susceptibility $\chi'_{\rm ac}$ whose position is strongly dependent on the value of $H_{\rm dc}$, in agreement with similar results obtained on both cuprate and pnictide superconductors [10, 11, 16–18]. Small values for the transition width Δ are detected independently on the value of $H_{\rm dc}$, namely $\Delta(90{\rm kOe}) \simeq 2\Delta(250{\rm Oe}) \simeq 0.4$ K. This striking sharpness hints towards the excellent quality of the sample, ensuring that the homogeneity of the Co-doping is extremely high. The sample is then an optimal ground for investigating the intrinsic features of the superconducting phase and of the motion of the vortex lines. Such drop in $\chi'_{\rm ac}$, in fact, is known to separate regions inside the thermodynamical superconducting phase where dissipative processes associated with the motion of vortex lines take place or not. In particular, due to the complex interplay of several factors like the mutual repulsion among vortices, the decreased amount of thermal energy and the interaction with lattice defects acting like pinning centers, in the low-T region the fluxoids turn into a glassy flux phase (GFP). Hence, deep into the GFP the superconductor is still able to effectively shield external magnetic fields [19, 20]. For the present sample, this can be deduced by the low-T saturation value $\chi'_{\rm ac} = -1/4\pi$ clearly indicating that the superconducting phase is extending over the total sample volume independently on $H_{\rm dc}$. On the other hand, in the high-T region (still for $T < T_{\rm c}$), mutual interactions and pinning mechanisms are no longer effective in comparison with thermal energies so that the fluxoids are basically free to move, leading to dissipation in turn. This is the so-called liquid flux phase (LFP).

In correspondence with the sharp drop of $\chi'_{\rm ac}$ the imaginary component $\chi''_{\rm ac}$ displays a single bell-shaped contribution peaked around a temperature value $T_{\rm P}$ also common to the maximum in $d\chi'_{\rm ac}/dT$ (see the inset of Fig. 1). This results from the matching of $\nu_{\rm m}$ to the inverse correlation time $1/\tau_{\rm c}$ characteristic of the motion of vortices through the crossover between GFP and LFP [10, 11, 16–18]. The most natural way to investigate in the vortex dynamics in detail is then to repeat $\chi_{\rm ac}$ vs. T scans at different $\nu_{\rm m}$ or, equivalently, to perform $\nu_{\rm m}$ scans at different T values across the GFP-LFP boundary. In the former case one extracts the $T_{\rm P}$ values from the position of the maxima of $\chi''_{\rm ac}$ vs. T curves at different $\nu_{\rm m}$ employing empirical peak functions around the maxima (see the close symbols in the main panel of Fig. 2 and the relative upper inset). In the latter case, one associates to the selected T the characteristic $\nu_{\rm m}$ value where a maximum in $\chi''_{\rm ac}$ appears (open symbols in Fig. 2, raw data not shown). Both kinds of measurements were performed on the considered single crystal, always confirming a sizeable dependence of $T_{\rm P}$ on $\nu_{\rm m}$. Given the extreme narrowness of the observed transitions, anyway, even uncertainties in the thermalization up to ±0.01 K can be detrimental for the latter measurements, as indicated by the wide error bars in Fig. 2. Correspondingly, a comparison between T-swept curves was chosen as the most reliable method by always keeping under the same conditions the slow warming rate through the transition.

If the degree of quenched disorder in the system is sizeable and, correspondingly, the density of pinning centers is high, thermally-activated processes are the leading mechanisms in driving the dynamical relaxation of the fluxoids. This results in a logarithmic dependence of $T_{\rm P}$ on $\nu_{\rm m}$ and is generally interpreted in terms of thermally-activated flux creep (TAFC) of the vortices [10, 11, 16]. In the presence of extremely pure and clean superconducting systems in the limit of weak disorder, on the other hand, the lower concentration of pinning centers makes the correlations and interaction among the vortices to clearly appear and to play a key role in the magnetic relaxation. This can allow, for instance, the detection of a scaling critical behaviour associated with a true thermodynamical phase transition between LFP and GFP. As it is well known, the fingerprint of the

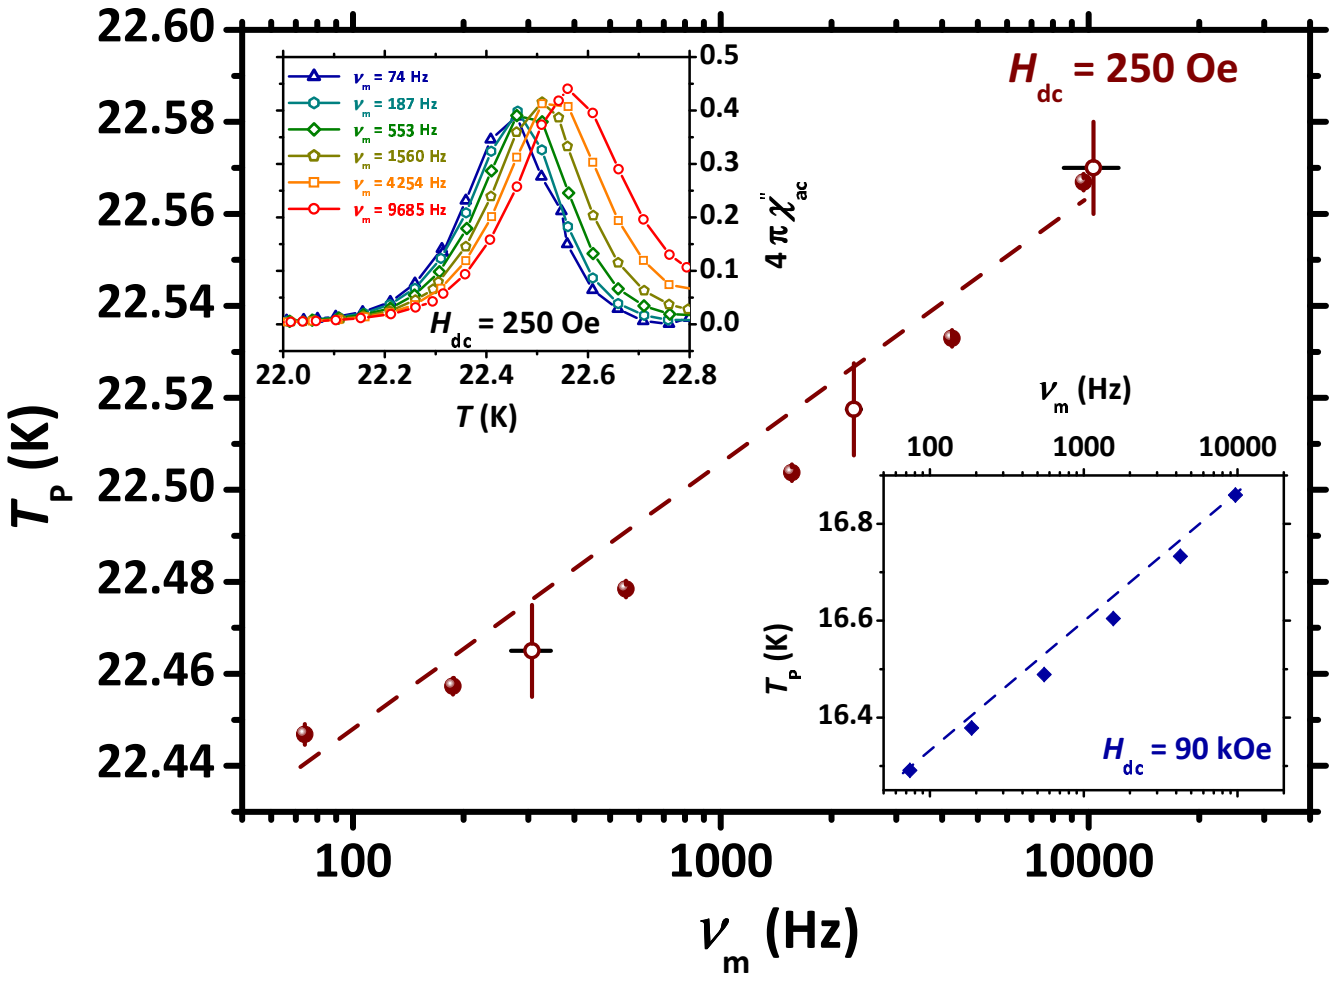

FIG. 2: (Color online) Main panel: position of the maximum in $\chi''_{\rm ac}$ vs. T curves as a function of $\nu_{\rm m}$ (full symbols). Open symbols refer to the estimates from isothermal $\chi''_{\rm ac}$ vs. $\nu_{\rm m}$ curves. The dashed line shows the expected logarithmic trend typical of thermally-activated processes. Data are taken at $H_{\rm dc} = 250$ Oe (data for $H_{\rm dc} = 90$ kOe are plotted in the lower inset with the same meaning of symbols). Upper inset: $\chi''_{\rm ac}$ vs. T at $H_{\rm dc} = 250$ Oe and at different $\nu_{\rm m}$.

critical behaviour is the appearance of power-law functional forms describing the trend of physical quantities as a function of some reduced variable quantifying the distance of the system from the critical point [21]. Our results clearly reveal such a scaling behaviour instead of a logarithmic one in the measured single crystal. In the case of $H_{\rm dc} = 250$ Oe shown in the main panel of Fig. 2, in fact, the departure from the dashed line (representing a guide to the eye for the expected trend emerging from a TAFC scenario) is extremely evident. The effect, even if less marked, is present also at higher values of the applied static field, as shown in the lower inset of Fig. 2 in the case of $H_{\rm dc} = 90$ kOe. Similarly to what is reported in the literature also in the case of cuprate superconductors (see Ref. 16), a weak dependence of $T_{\rm P}$ on $\nu_{\rm m}$ has been detected even at the nominal $H_{\rm dc} = 0$ Oe value (in the present sample, the variation of $T_{\rm P}$ at $H_{\rm dc} = 0$ Oe over the entire range of $\nu_{\rm m}$ is less than 0.05 K). Nevertheless, it is stressed that such effect should be considered as spurious mainly due to strong demagnetization effects (associated with the high value of $D_{\rm m}$) possibly enhancing the sum of both $H_{\rm ac}$ and any residual component of $H_{\rm dc}$ to effective values close to $H_{\rm c1}$.

With reference to the model discussed in Refs. 1, 22, one can assume that the transition of vortices from LFP to GFP occurs at a critical value $T_{\rm g}$ dependent on the value of the external static field. From dynamical scaling considerations the following relation can be derived for the reduced temperature $\varepsilon_{\rm g}(\nu_{\rm m})$

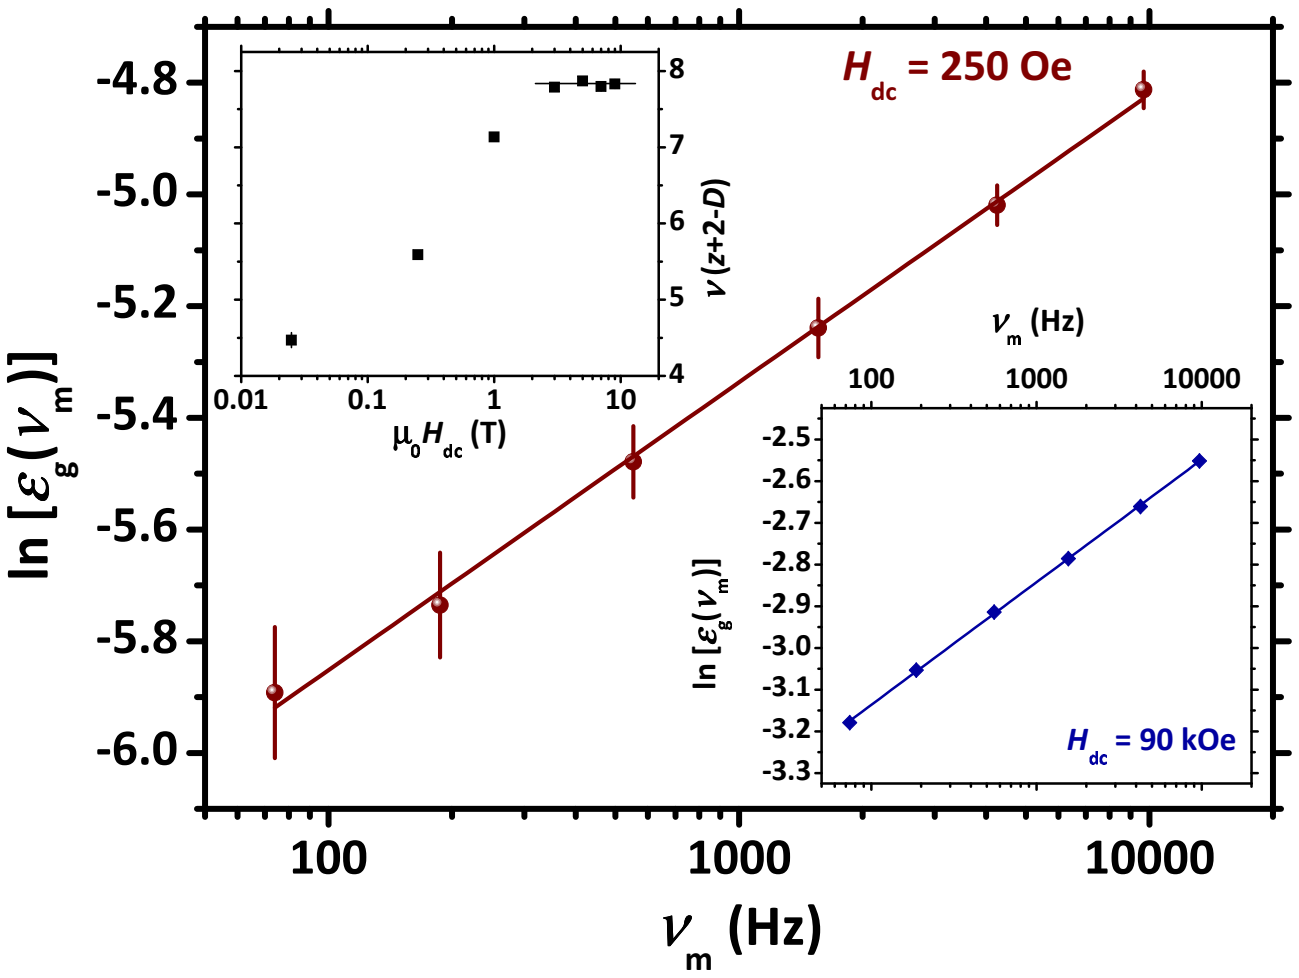

FIG. 3: (Color online) Main panel: $T_{\rm P}$ vs. $\nu_{\rm m}$ data at $H_{\rm dc} = 250$ Oe (already plotted in the main panel of Fig. 2) after analysis according to Eq. (1) (see continuous line). The data for $H_{\rm dc} = 90$ kOe have been reported in the lower inset as in Fig. 2 (the error bars are within the symbols). Upper panel: dependence of the critical exponent on $H_{\rm dc}$.

$$\varepsilon_{\rm g}(\nu_{\rm m}) \equiv \frac{T_{\rm P}(\nu_{\rm m}) - T_{\rm g}}{T_{\rm g}} = \left(\frac{\nu_{\rm m}}{\nu_0}\right)^{1/[\nu(z+2-D)]} \qquad (1)$$

where $T_{\rm P}(\nu_{\rm m})$ is straightforwardly derived from the maxima in $\chi''_{\rm ac}$ vs. T curves as discussed above. The parameter ν_0 in this expression is a microscopic characteristic attempt frequency with a typical value in the THz range. The dimensionality of the system is indicated by D while z and ν are the dynamical and static critical exponent for the vortex-glass correlation time and length, respectively. One can then deduce the values for $T_{\rm g}$ at the different values of $H_{\rm dc}$ from plotting the data presented in the main panel of Fig. 2 according to Eq. (1). The accuracy associated with the assessment of $T_{\rm g}$ values is remarkably high (~ 0.01 K) since, by taking values beyond this range, results clearly deviate from the power-law behaviours evidenced in Fig. 3 (both main panel and lower inset). This high precision in the estimate of $T_{\rm g}$ allows us to sizeably reduce the mutual statistical dependence among the fitting parameters in Eq. (1).

The results of the fitting procedure of the experimental data are in good agreement with theoretical expectations. The attempt frequency ν_0, in particular, is found to take values $\nu_0 \sim 10^{13} \div 10^{15}$ Hz slightly higher than other reports in the literature but nonetheless reasonable. The dependence of the critical exponent on $H_{\rm dc}$, on the other hand, is shown in the upper inset of Fig. 3. Most interestingly, a systematic increase can be discerned with increasing $H_{\rm dc}$ until the saturation value 7.8±0.2 is reached for $H_{\rm dc} \gtrsim 20$ kOe. This saturation value is in close agreement with previous reports on cuprate compounds like

$YBa_2Cu_3O_7$ and $Bi_2Sr_2CaCu_2O_{8+\delta}$ [3, 22–24] where values $\sim 6.5 \div 8$ are typically reported. On the other hand, the large change evidenced in the low-field regime cannot be explained in terms of a crossover between different values of dimensionality for the vortex phase. Following the arguments reported in Ref. 24, in fact, one can estimate the typical magnetic field inducing such dimensionality crossover as $H_{\rm cr} \sim 4\Phi_0/d^2\gamma^2$. For the inter-plane distance one can assume $d \simeq 6.5$ Å (see, for instance, Ref. 6 and references therein) while $\gamma \simeq 2$ holds [25], resulting in $H_{\rm cr}$ values as high as 5×10^7 Oe. This is similar to the case of 1111 compounds even if, in that case, the field dependence of the critical exponent is the opposite of what is observed here [8]. Our results instead closely resemble what is reported in the case of twinned crystals of $YBa_2Cu_3O_{7-\delta}$ where the field-dependence of the critical exponent typically shows sudden step-like increase at some characteristic field values of the order of few Teslas [26, 27]. The interpretation of the results in those cases are typically given in terms of a crossover between different types of glass phases in relation with the typical dimensionality of crystalline defects. Further studies on the present single crystals are needed in order to gain more insights into the detailed features of vortex pinning and their connection to the resulting glassy phase. In this respect, as discussed in previous reports about MgB_2 samples [28], it should be anyway stressed that low values of magnetic field ($H_{\rm dc} \lesssim 10$ kOe) are expected to favour the emergence of a Bragg-like glassy phase in presence of weak degrees of quenched disorder [29] and, in turn, to lead to a decrease of the values of critical exponents. This well agrees with our results and strongly supports the same scenario in $Ba(Fe_{0.9}Co_{0.1})_2As_2$. The high-field region characterized by $\nu\,(z + 2 - D) \simeq 7.8$ is then associated to a glass state with a higher degree of amorphousness (see Fig. 4).

The $T_{\rm g}$ values estimated from the fitting procedure according to Eq. (1) are plotted as a function of the magnetic field in Fig. 4. As reported in the same graph, their dependence on the corresponding $H_{\rm dc} = H_{\rm g}$ values can be nicely fit by a mean-field like function $[T_{\rm c}(0) - T_{\rm g}] \propto (H_{\rm g})^{1/\beta}$ with the fitting parameter $\beta = 1.30 \pm 0.05$ in excellent agreement with the expected result $\beta = 4/3$ from the vortex-glass model for $D = 3$ and with previous reports in $YBa_2Cu_3O_7$ [1, 23]. According to the model discussed in Ref. 29, further measurements of magnetic ac susceptibility at higher values of magnetic field allowing to detect a critical endpoint of this transition line could possibly further check the validity of the Bragg-glass scenario described above. Results for $T_{\rm g}\,(H_{\rm dc})$ are completed by the T-dependence of $H^{\rm c}_{\rm c2}$ in Fig. 4. Experimental points have been derived from measurements of FC magnetization at different $H_{\rm dc}$ values by means of a Quantum Design vibrating-sample SQUID magnetometer (the fitting procedure of the diamagnetic onset has been described previously in Ref. 11). The relative raw data are not shown. A linear fitting of the data leads to a slope value -2.50 ± 0.05 T/K, in perfect agreement with previous reports on different single crystals of $Ba(Fe_{1-x}Co_x)_2As_2$ [25].

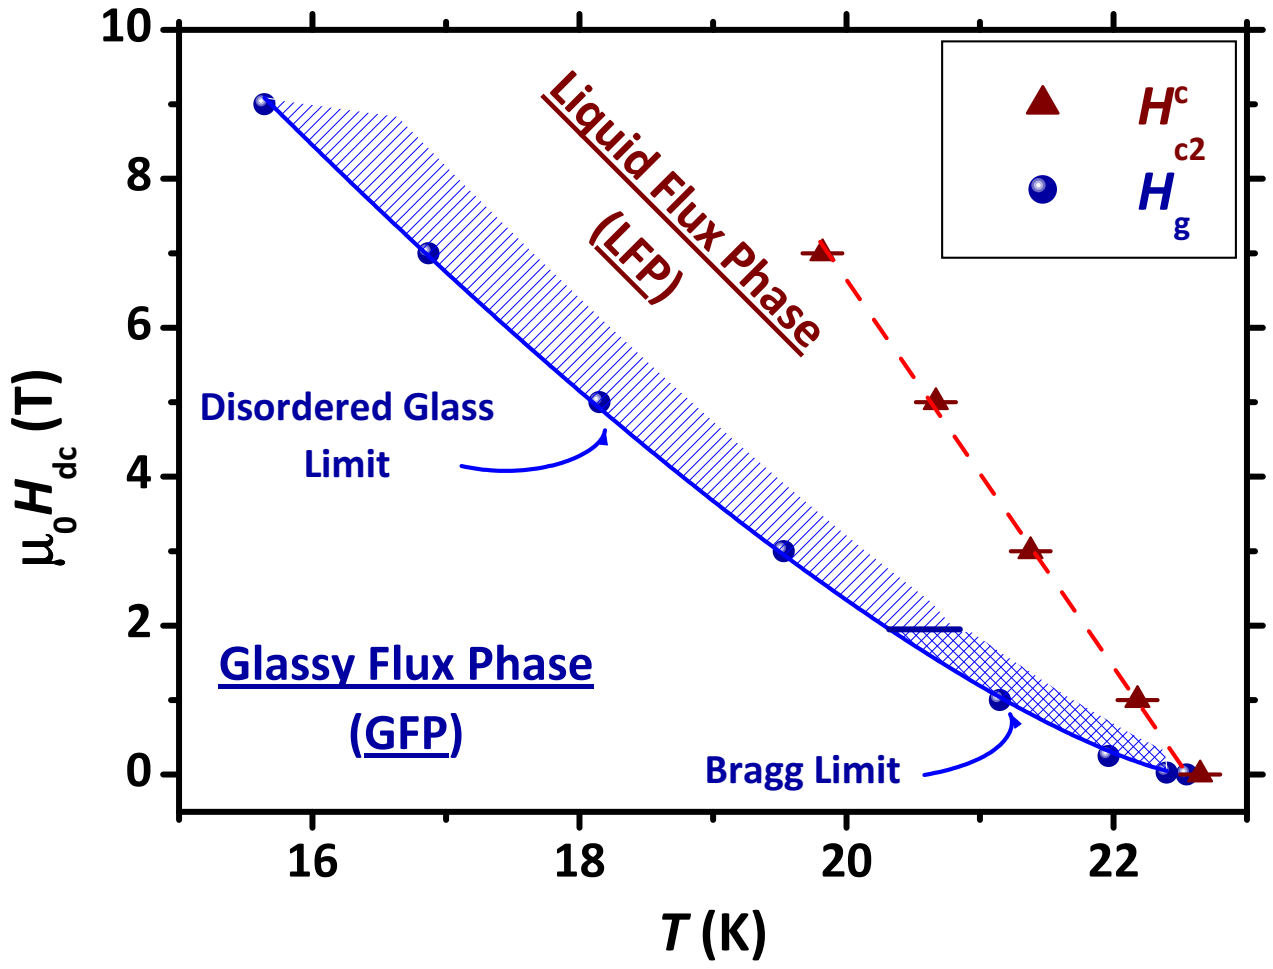

FIG. 4: (Color online) Phase diagram for the superconducting state of $Ba(Fe_{0.9}Co_{0.1})_2As_2$. The continuous line is a fit to the $H_{\rm g}$ data according to the mean-field function discussed in the text. The shaded areas refer to the two different regimes for the dependence of the critical exponent on $H_{\rm dc}$ presented in the upper inset of Fig. 3 and discussed in the text. The dashed line is a linear fit to the $H^{\rm c}_{\rm c2}$ data (see text).

In summary, the extremely high quality of the investigated single crystal of superconducting $Ba(Fe_{0.9}Co_{0.1})_2As_2$ allows us to evidence by means of magnetic ac susceptibility measurements a critical behaviour associated with the phase transition of vortex lines from liquid to glassy states. Results in the high-field regime are in quantitative agreement with typical reports for cuprate superconductors, suggesting a shared underlying physics for both kinds of high-$T_{\rm c}$ superconductors. The field-dependence of the critical exponent cannot be explained in terms of any dimensionality crossover for the vortex phase. Instead, the results suggest a non-trivial transition among different types of glassy-states, where the degree of amorphousness is decreased towards the limit of Bragg-glass with decreasing the magnetic field. Our results open the way to a more detailed investigation of the physics of vortices across the phase diagram of $Ba(Fe_{1-x}Co_x)_2As_2$. The evolution of the degree of glassiness and its possible interplay with magnetic fluctuations arising from the progressively enhanced nesting of the Fermi surface with reducing x, in particular, could be an extremely peculiar study based on our present data.

Stimulating discussions with P. Carretta and S. Singh are gratefully acknowledged. The authors thank M. Deutschmann, S. Pichl and S. Gaß for technical support.

Work was supported by the Deutsche Forschungsgemeinschaft DFG through the Priority Programme SPP1458 (Grants No. BE1749/13). S. W. acknowledges support by DFG under the Emmy-Noether programme (Grant No. WU595/3-1).

---

* E-mail: g.prando@ifw-dresden.de

[1] D. S. Fisher, M. P. A. Fisher, D. A. Huse, *Phys. Rev.* **B 43**, 130 (1991)

[2] G. Blatter, M. V. Feigel'man, V. B. Geshkenbein, A. I. Larkin, V. M. Vinokur, *Rev. Mod. Phys.* **66**, 1125 (1994)

[3] R. H. Koch, V. Foglietti, W. J. Gallagher, G. Koren, A. Gupta, M. P. A. Fisher, *Phys. Rev. Lett.* **63**, 1511 (1989)

[4] D. J. Bishop, P. L. Gammel, D. A. Huse, C. A. Murray, *Science* **255**, 165 (1992)

[5] Y. Kamihara, T. Watanabe, M. Hirano, H. Hosono, *J. Am. Chem. Soc.* **130**, 3296 (2008)

[6] D. C. Johnston, *Adv. Phys.* **59**, 803 (2010)

[7] R. Prozorov, N. Ni, M. A. Tanatar, V. G. Kogan, R. T. Gordon, C. Martin, E. C. Blomberg, P. Prommapan, J. Q. Yan, S. L. Bud'ko, P. C. Canfield, *Phys. Rev.* **B 78**, 224506 (2008)

[8] H.-S. Lee, M. Bartkowiak, J. S. Kim, H.-J. Lee, *Phys. Rev.* **B 82**, 104523 (2010)

[9] A. K. Pramanik, L. Harnagea, S. Singh, S. Aswartham, G. Behr, S. Wurmehl, C. Hess, R. Klingeler, B. Büchner, *Phys. Rev.* **B 82**, 014503 (2010)

[10] G. Prando, P. Carretta, R. De Renzi, S. Sanna, A. Palenzona, M. Putti, M. Tropeano, *Phys. Rev.* **B 83**, 174514 (2011)

[11] G. Prando, P. Carretta, R. De Renzi, S. Sanna, H.-J. Grafe, S. Wurmehl, B. Büchner, *Phys. Rev.* **B 85**, 144522 (2012)

[12] S. R. Ghorbani, X. L. Wang, M. Shahbazi, S. X. Dou, K. Y. Choi, C. T. Lin, *Appl. Phys. Lett.* **100**, 072603 (2012)

[13] L. Bossoni, P. Carretta, A. Thaler, P. C. Canfield, *Phys. Rev.* **B 85**, 104525 (2012)

[14] E. Pardo, D.-X. Chen, A. Sanchez, *J. Appl. Phys.* **96**, 5365 (2004)

[15] S. Aswartham, C. Nacke, G. Friemel, N. Leps, S. Wurmehl, N. Wizent, C. Hess, R. Klingeler, G. Behr, Büchner, *J. Cryst. Growth* **314**, 341 (2011)

[16] A. P. Malozemoff, T. K. Worthington, Y. Yeshurun, F. Holtzberg, P. H. Kes, *Phys. Rev.* **B 38**, 7203(R) (1988)

[17] T. T. M. Palstra, B. Batlogg, R. B. van Dover, L. F. Schneemeyer, J. V. Waszczak, *Phys. Rev.* **B 41**, 6621 (1990)

[18] M. Tinkham, *Physica* **B 169**, 66 (1991)

[19] E. H. Brandt, *Phys. Rev. Lett.* **67**, 2219 (1991)

[20] M. W. Coffey, J. R. Clem, *Phys. Rev.* **B 45**, 9872 (1992)

[21] H. E. Stanley, *Introduction to Phase Transitions and Critical Phenomena*, Oxford University Press (1971)

[22] P. L. Gammel, *J. Appl. Phys.* **67**, 4676 (1990)

[23] P. L. Gammel, L. F. Schneemeyer, D. J. Bishop, *Phys. Rev. Lett.* **66**, 953 (1991)

[24] H. Safar, P. L. Gammel, D. J. Bishop, D. B. Mitzi, A. Kapitulnik, *Phys. Rev. Lett.* **68**, 2672 (1992)

[25] A. Yamamoto, J. Jaroszynski, C. Tarantini, L. Balicas, J. Jiang, A. Gurevich, D. C. Larbalestier, R. Jin, A. S. Sefat, M. A. McGuire, B. C. Sales, D. K. Christen, D. Mandrus, *Appl. Phys. Lett.* **94**, 062511 (2009)

[26] B. Maiorov, E. Osquiguil, *Phys. Rev.* **B 64**, 052511 (2001)

[27] T. Naito, H. Iwasaki, T. Nishizaki, N. Kobayashi, *Phys. Rev.* **B 70**, 014515 (2004)

[28] M. B. Maple, B. J. Taylor, S. Li, N. A. Frederick, V. F. Nesterenko, S. S. Indrakanti, *Phys.* **C 387**, 131 (2003)

[29] T. Nattermann, S. Scheidl, *Adv. Phys.* **49**, 607 (2000)